

**EMISSIONS CONTROL CATALYSTS: LINKS BETWEEN FECRALLOY
PREOXIDATION AND COATING ADHERENCE**

Stephen A. Adegbite^{a*}

***^a School of Chemical Engineering, University of Birmingham, Edgbaston,
Birmingham B15 2TT, United Kingdom***

* Corresponding author Dr S.A. Adegbite, tel: +44(0)1216045143, email: stephen_adegbite@hotmail.com

Abstract

Tightening emissions legislation for vehicles across the world has caused the use of monolith catalysts in automobile emission control to become ubiquitous. In this study, the physiochemical transformations caused by thermal pre-oxidation of the surface of Fecralloy[®] foil, an integral component of emissions control catalysts, have been studied to assess their role on coating film adherence. The foil coupons were pre-oxidised at 950 °C for 0, 5, 10 and 30 h and the mass gain was found to fit a simplified hyperbolic model. Measurements were made of surface topography and microstructure using laser profiling interferometry (LPI) and scanning electron microscopy (SEM), with chemical analysis being obtained from X-ray diffraction (XRD). The optimal surface roughness was obtained after 10 h of pre-oxidation, when the surface contained significant amounts of α -alumina arranged as randomly oriented whiskers. Upon coating of the treated foil coupons with γ -alumina slurry, the sample pre-oxidised for 10 hours gave the best performance in terms of coating film loading of 7.94 mass % and adherence of less than 10 mass % loss.

Key words: catalyst, Fecralloy[®], pre-oxidation, alumina, coating, adherence

1. Introduction

Tightening emissions legislation for vehicles across the world has caused the use of monolith catalysts in automobile emission control to become ubiquitous. Their impact has been considerable, with emission levels from exhaust systems of passenger cars falling by more than 90% since 1975, and with zero emissions now a future target. Environmentally harmful carbon monoxide and oxides of nitrogen in the exhaust stream are converted inside the monolith catalyst into carbon dioxide and nitrogen (Acres and Harrison, 2004; Twigg, 2006).

Monoliths are structures comprised of multiple parallel channels. One method of producing monolith catalysts is to coat the monolith surfaces with γ -alumina film containing active species (usually platinum group metals, PGMs, such as Pt, Pd and Rh). Monoliths are generally made from either metallic or ceramic materials, the former from thin metal sheet such as Fecralloy[®], the focus of this study, and the latter typically from cordierite (Avila *et al.*, 2005). Fecralloy[®] is comprised essentially of iron, Fe, chromium, Cr, and aluminium, Al. It is well suited for catalyst support applications because of its high mechanical strength, thermal conductivity and ductility which make it easy to process. It clearly outperforms cordierite as a monolith material in all these crucial properties (Hickman and Schmidt, 1992b; Hickman and Schmidt, 1992a).

To ensure adherence of the γ -alumina coatings, Fecralloy[®] has to be pre-oxidised which changes its surface topography to provide a rough surface (Cybulski and Moulijn, 2006). Pre-oxidation also provides enrichment of the Fecralloy[®] surface with aluminium, therefore prolonging the product component life (Nicholls and Quadackers, 2002).

Some studies have assessed the effects of pre-oxidation on dip-coated foil coupons, by relating the surface microstructure obtained by scanning electron microscopy (SEM) to the coating adherence (e.g. Jia *et al.*, 2007; Zhao *et al.*, 2003). However, these comparisons are somewhat qualitative in nature and do not consider a quantitative measure of the surface roughness, nor do they address coating at a controlled shear rate. In this new study, a detailed assessment of Fecralloy[®] two-dimensional (2D) and three-dimensional (3D) surface topography by laser profiling interferometry (LPI) was performed as a function of pre-oxidation conditions. In addition, SEM and X-ray diffraction (XRD) techniques have been applied to give a comprehensive description of the physiochemical transformations caused by pre-oxidation. To determine the effect of pre-oxidation on coating film adherence, γ -alumina slurry was deposited onto the Fecralloy[®] foil coupons at a controlled shear rate using an automatic film applicator, and the resulting composites were dried and calcined afterwards. The coating film loading and adherence were determined to reveal the optimal pre-oxidation conditions.

2. Materials and Methods

2.1. Pre-treatment and assessment of Fecralloy[®] foil

Commercially available Fecralloy[®] foil (GoodFellow, UK) of 50 µm thickness with a composition of Fe (72.6 wt %), Cr (22.0 wt %), Al (4.80 wt %), Y (0.30 wt %) and Si (0.30 wt %) was used. The foil was cut into 50 mm × 80 mm coupons. The pre-treatment of the coupons consisted of the following steps (Jia *et al.*, 2007):

- *Degreasing*: ultrasonic cleaning at room temperature in acetone bath for 10 min, and then with deionised water at 80 °C for 10 min
- *Pre-oxidation*: thermal oxidation in a furnace (Lenton, UK) at 950 °C for different durations: 0, 5, 10 and 30 h

The specific mass gain of the coupons as a function of pre-oxidation time was determined using a mass balance (Ohaus Corporation, USA). The surface topography (namely surface roughness and topography profiles) of the coupons was measured by LPI (Taylor Hobson, UK). The interferometer measured 1000 sampling lengths of 5 µm each, thus, covering a total evaluation length of 5 mm. The surface chemical composition of the coupons was determined by XRD using X' Pert Pro diffractometer (Phillips, The Netherlands) having Fe-filtered Co K α radiation and a power of 45 kV × 30 mA. The surface microstructure of the coupons was assessed by using a JEOL 6060 SEM (Oxford Instruments, UK).

2.2. Coating of foils by an automatic film applicator

A γ -alumina slurry of average diameter $d_{0.5} = 4.36 \mu\text{m}$ and solids concentration of 40 wt% was prepared at a pH of 4 using ethanoic acid solution (Fischer Scientific, UK). The slurries were deposited onto the Fecralloy[®] coupons using an automatic film applicator (Sheen Instruments, UK) which provided close control of the traverse coating speed (Adegbite, 2010). The slurries were drawn across the coupons at a traverse speed of 100 mms^{-1} with a wire-wound bar of $100 \mu\text{m}$ gap [Fig. 1(a)]. The coated coupons were allowed to dry at room temperature, and were then oven dried at 110°C for 1 h and finally calcined at 500°C for 1 h (Jia *et al.*, 2007). The surface view of a product coating obtained by SEM is shown in Fig. 1(b).

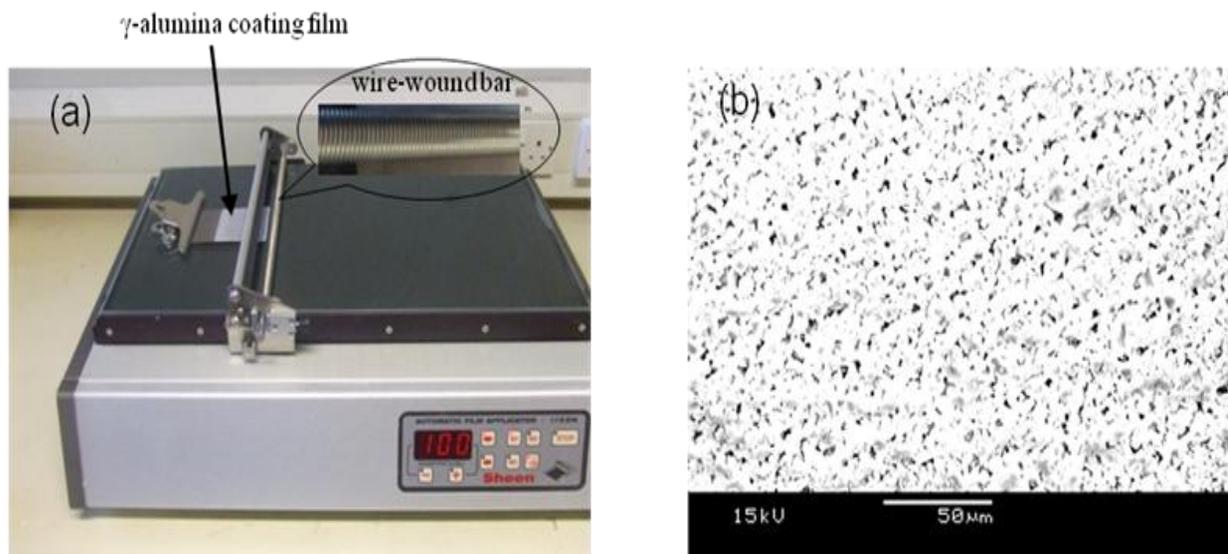


Fig. 1. Coating of Fecralloy[®] supports: (a) γ -alumina coating film applied by 1132N applicator; (b) SEM micrograph of coating surface.

2.3. Assessment of coatings

The coating film loading on the Fecralloy[®] surface was then calculated by the percentage mass increase of the coupon. To determine coating film adherence, the coated foils were soaked into petroleum ether contained inside a sealed beaker for 30 min, then soaked in an ultrasonic bath (300 W and 60 kHz) for 1 h and later dried in an oven at 110°C for 2 h (Valentini *et al.*, 2001). The percentage mass loss was then calculated, meaning that the lower the mass loss the better the coating adherence.

3. Results and Discussion

3.1. Pre-oxidation profile

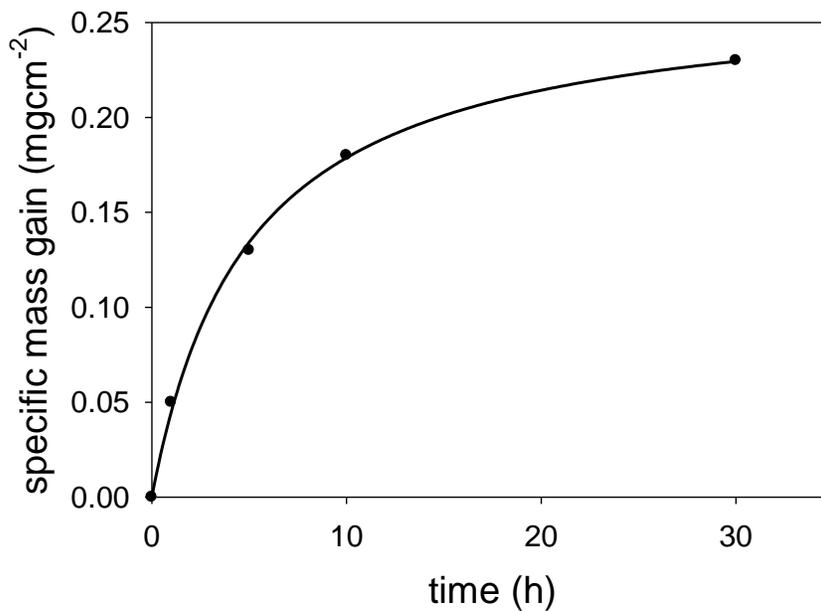


Fig. 2. Pre-oxidation profile of Fecralloy[®] coupons for 0 – 30 h.

The pre-oxidation profile shown in Fig. 2 represents the specific mass gain by foils as a function of pre-oxidation time. The increase in the specific mass of the foil with pre-oxidation time arises from the continuous formation of oxide layers on the foil surface. It is shown that the rate of oxide formation, which is the gradient of the curve, was highest at the start of pre-oxidation, and it progressively diminished as pre-oxidation continued. A simplified hyperbolic model (Eq. 1), derived from a previous study (Pragnell *et al.*, 2005), properly describes the pre-oxidation profile of Fecralloy[®] for 0 – 30 h.

$$\overline{\Delta m} = \frac{Xt}{Y + t} \quad (1)$$

where, $\overline{\Delta m}$ is specific mass gain (mgcm⁻²) and t is pre-oxidation time (h).

Constants X and Y were found to be 0.27 and 5.0 respectively.

3.2. Topography characterisation of Fecralloy[®] coupons by LPI

The surface topography of the coupons, represented by the 2D and 3D roughness parameters and the topography profiles, are shown in Table 1 and Fig. 3. The roughness parameters for the untreated coupon were very low because the surface has not been transformed. The roughness parameters increased significantly after 5 h pre-oxidation, then reached the peak at 10 h pre-oxidation and later declined upon prolonged pre-oxidation for 30 h (see Table 1). Clearly, the Fecralloy[®] coupon pre-oxidised at 950 °C for 10 h had the roughest surface; this is supported by the textural profiles shown in Fig. 3. Coating film adherence is promoted by rough surfaces which act as glues for coatings because of their irregularities. The profiles shown in Fig. 3 also exhibit order in their surface structure due to fabrication patterns, this is particularly

evident in the sample shown in Fig. 3(c) which is characterised by deep penetrating grooves.

Table 1. Roughness parameters of coupons pre-oxidised at 950 °C for 0 – 30 h

Roughness parameters	Type	Definition	Values (µm)			
			0 h	5 h	10 h	30 h
R _a	2D	arithmetic mean	0.06	0.15	0.31	0.23
R _q	2D	root mean square	0.08	0.17	0.36	0.20
S _a	3D	arithmetic mean	0.20	0.35	0.83	0.52
S _q	3D	root mean square	0.24	0.42	1.01	0.69

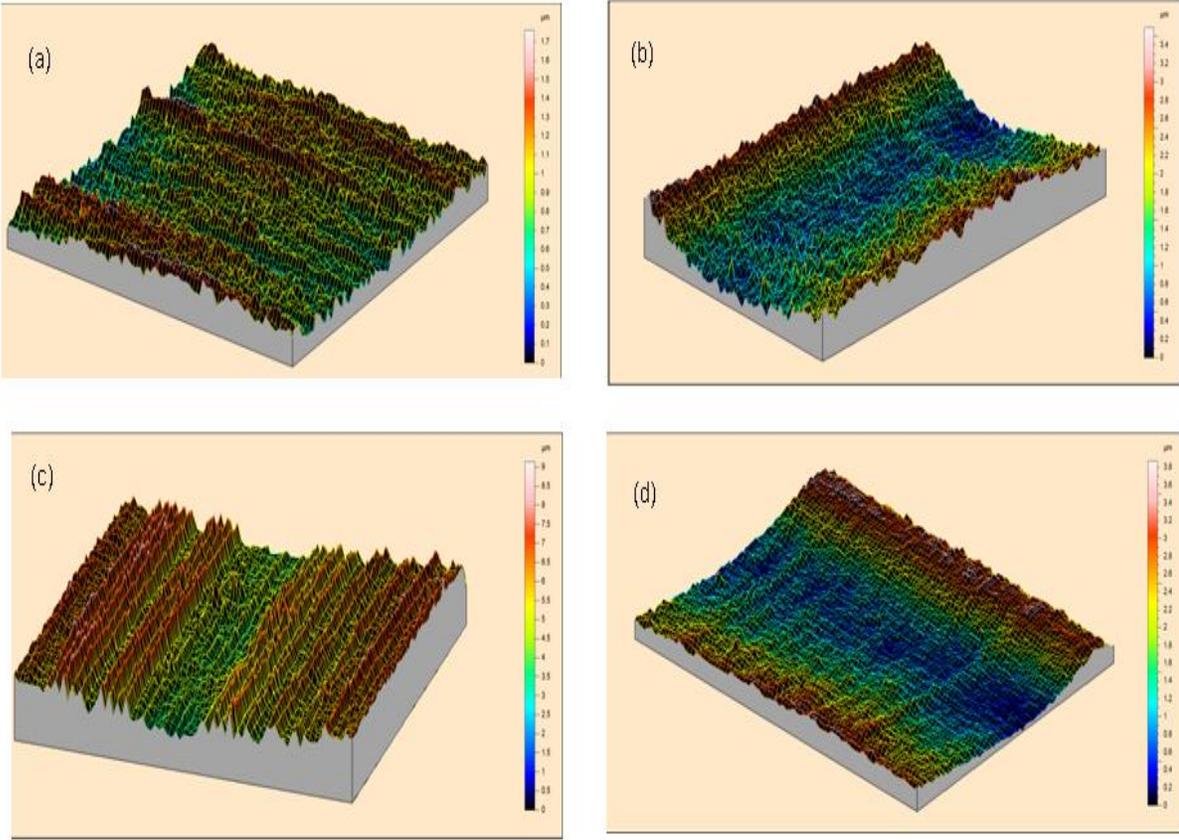


Fig. 3. Topography profiles of Fecralloy[®] coupons pre-oxidised at 950°C for (a) 0 h; (b) 5 h; (c) 10 h; and (d) 30 h.

3.3. XRD analysis of Fecralloy[®] surface

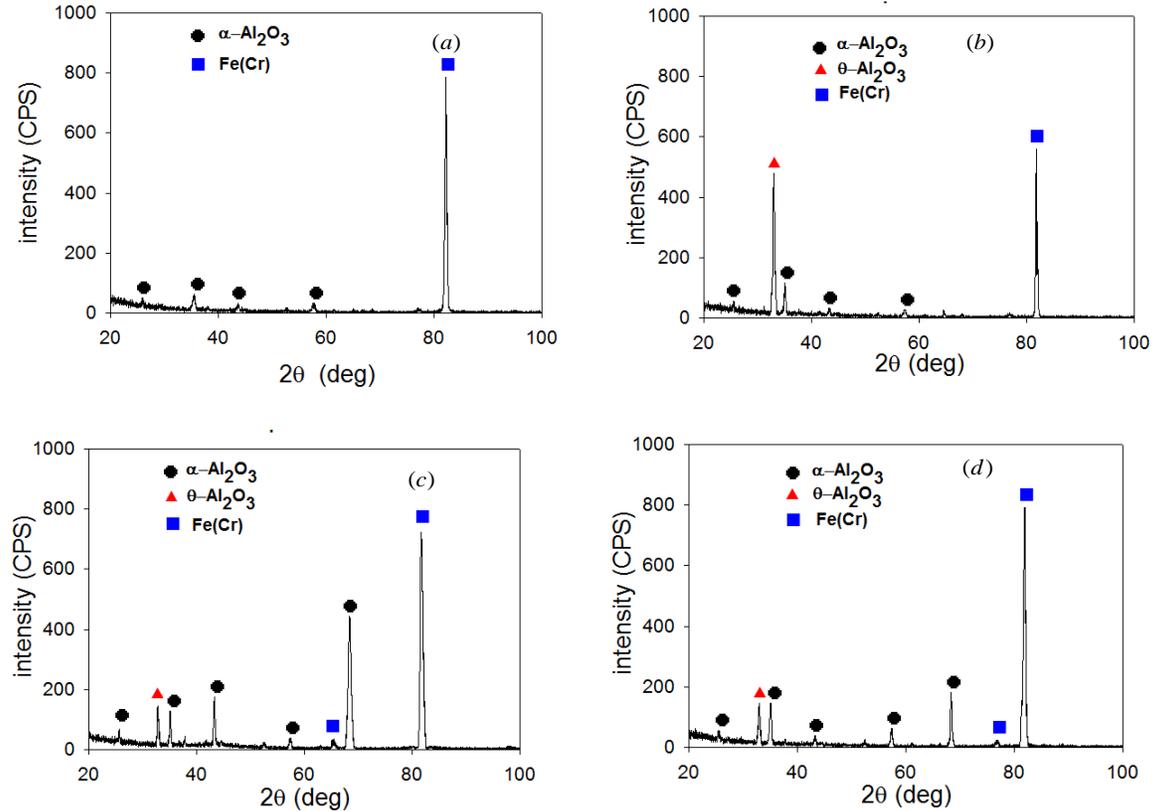


Fig. 4. XRD patterns of Fecralloy[®] coupons pre-oxidised at 950°C for (a) 0 h; (b) 5 h; (c) 10 h; and (d) 30 h.

The XRD patterns in Fig. 4 show the surface chemical composition of the coupons pre-oxidised at 950 °C for 0 – 30 h. The untreated coupon comprises of a Fe (Cr) peak and some α -alumina peaks, which are present in small amounts [Fig. 4(a)]. Pre-oxidation for 5 h produced substantial amounts of α -alumina and a small amount of θ -alumina [Fig. 4(b)]. Increased pre-oxidation to 10 h produced sufficient transformation of θ -alumina into α -alumina, as the peaks of the latter are large and conspicuously visible [Fig. 4(c)]. Prolonged pre-oxidation however resulted into formation of α -alumina conglomerates as other alloy elements are spontaneously oxidised; this is characterized by diminishing peaks of α -alumina [Fig. 4(d)]. The Fecralloy[®] surface enrichment by aluminium during

pre-treatment is caused by an elemental transport process (Jia *et al.*, 2007; Nicholls and Quadackers, 2002).

3.4. Assessment of Fecralloy[®] surface microstructure by SEM

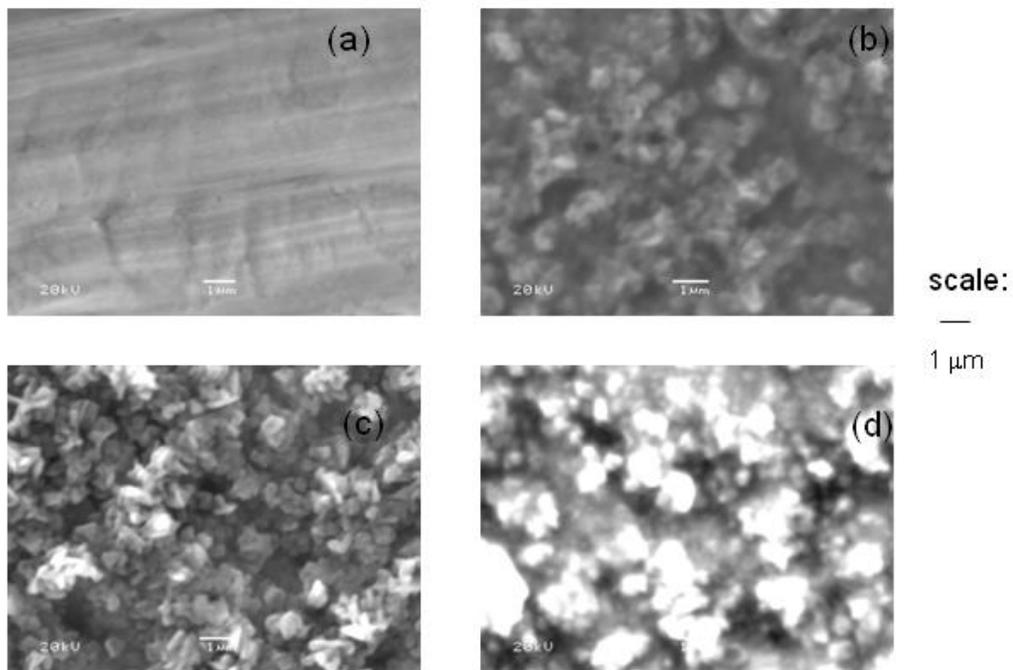


Fig. 5. SEM micrographs of Fecralloy[®] coupons pre-oxidised at 950°C for (a) 0; (b) 5; (c) 10 and (d) 30 h.

The SEM micrographs displayed in Fig. 5 clearly show the distinctions between the surface morphologies of the untreated and pre-oxidised coupons. The untreated coupon [Fig. 5(a)] has a plain surface with no significant microstructure while the pre-oxidised coupons contain α -alumina whiskers [Fig. 5(b) – (d)]. After 5 h of pre-oxidation, there exists trace amounts of α -alumina. However, the coupon pre-oxidised for 10 h was characterized by uniform, conspicuous and randomly oriented α -alumina whiskers. It is shown that at this condition the α -alumina are properly formed and arranged in a manner which positions them for good adhering capabilities (Avila *et al.*, 2005). The

attendant effect of pre-oxidation for up to 30 h was the formation of non-uniform conglomerates of α -alumina.

3.5. Coating loading and adherence

The coating film loading and weight loss from adherence test are shown in Table 2. The values were averaged over 5 measurements with a standard deviation (SD) within 3.5%. Clearly, the duration of pre-oxidation has a major influence on the adherence of the coating film on the Fecralloy[®] coupons.

Table 2. Coating properties for Fecralloy[®] coupons pre-oxidised at 950 °C for 0 – 30 h.

Pre-oxidation time (h)	Coating loading (mass %) SD = ± 3.1 % loading	Mass % loss from adherence test SD = ± 3.5 % of loss
0	0.08	99.6
5	5.19	19.4
10	7.94	9.90
30	6.75	16.3

The results in Table 2 can be explained in the light of the Fecralloy[®] surface characterization discussed above in sections 3.2 – 3.4. For the untreated coupon, the coating loading and adherence were very poor because the foil surface was the least rough and no wettability occurred. The coupons pre-oxidised for 5 and 30 h showed improved capabilities which are commensurate with their roughness characteristics in section 3.2. The optimal coating loading and adherence were obtained from the coupon

with the roughest surface i.e. the sample pre-oxidised for 10 h. This is because of the enhanced surface microstructure brought about by the randomly oriented α -alumina whiskers, thereby creating a suitable topography onto which coating film is firmly anchored. The images of the coatings after the adherence test are also given in Fig. 6 which revealed the weakened areas where coatings had been lost.

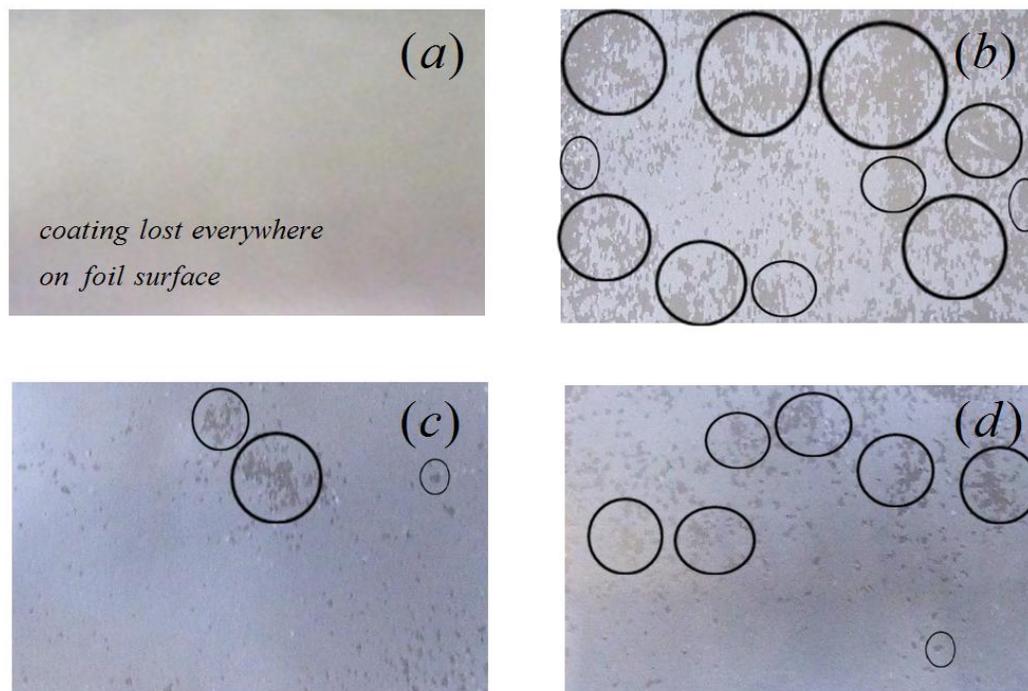


Fig. 6. Coatings on Fecralloy[®] coupons after adherence test (circles indicating some areas of coating loss): (a) 0; (b) 5; (c) 10 and (d) 30 h.

4. Conclusions

Fecralloy[®] foils are materials from which monolith emissions catalysts are made. The Fecralloy[®] pre-oxidation conditions have been shown to be central to achieving increased performance, in terms of coating film loading and adherence. A simplified hyperbolic model provided the best fit for specific mass gain by the coupons as a

function of pre-oxidation time from 0 – 30 h. The optimal coating film loading (7.94 mass %) and adherence (9.90 mass % loss) were obtained from coupons pre-oxidised at 950 °C for 10 h, as these conditions produced the optimal surface topography and microstructure.

The Author

Stephen Adegbite has a background in Chemical Engineering from the University of Birmingham, UK. He completed a PhD in Material Science, which focused on the optimisation of alumina coatings supported on metallic supports for automotive emissions control.

Acknowledgements

This research was supported by the Engineering and Physical Sciences Research Council (EPSRC) in the UK.

References

1. Acres,G.J.K., Harrison,B. (2004). The development of catalysts for emission control from motor vehicles: early research at Johnson Matthey. *Topics in Catalysis*. **28**: 3-11.
2. Adegbite,S.A. (2010). Coating of catalyst supports: links between slurry characteristics, coating process and final coating quality, Ph.D. Thesis. *University of Birmingham*. pp. 131-132.
3. Avila,P., Montes,M., Miro,E.E. (2005). Monolithic reactors for environmental applications - a review on preparation technologies. *Chemical Engineering Journal*. **109**: 11-36.
4. Cybulski,A., Moulijn,J.A. (2006) Metal and coated metal catalysts. In: *Structured catalysts and reactors*. pp. 71-105. Taylor & Francis, London.
5. Hickman,D.A., Schmidt,L.D. (1992a). Synthesis gas-formation by direct oxidation of methane over Pt monoliths. *Journal of Catalysis*. **138**: 267-282.
6. Hickman,D.A., Schmidt,L.D. (1992b). The role of boundary-layer mass-transfer in partial oxidation selectivity. *Journal of Catalysis*. **136**: 300-308.
7. Jia,L.W., Shen,M.Q., Wang,J. (2007). Preparation and characterization of dip-coated γ -alumina based ceramic materials on FeCrAl foils. *Surface & Coatings Technology*. **201**: 7159-7165.

8. Nicholls, J.R., Quadackers, W.J. (2002) Materials issues relevant to the development of future metal foil automotive catalytic converters. In: *Materials aspects in automotive catalytic converters*. Bode H (ed), pp. 31. Wiley-VCH, Weinheim.
9. Pragnell, W.M., Evans, H.E., Naumenko, D., Quadackers, W.J. (2005). Aluminium depletion in FeCrAlY steel during transitional alumina formation. *Materials at High Temperatures*. **22**: 561-566.
10. Twigg, M.V. (2006). Roles of catalytic oxidation in control of vehicle exhaust emissions. *Catalysis Today*. **117**: 407-418.
11. Valentini, M., Cristiani, G., Levi, M., Tronconi, E., Forzatti, P. (2001). The deposition of γ -Al₂O₃ layers on ceramic and metallic supports for the preparation of structured catalysts. *Catalysis Today*. **69**: 307-314.
12. Zhao, S., Zhang, J.Z., Weng, D., Wu, X.D. (2003). A method to form well-adhered γ -Al₂O₃ layers on FeCrAl metallic supports. *Surface & Coatings Technology*. **167**: 97-105.